

A Granular Inorganic Adsorbent Highly Selective to Cesium – 15058

Li-Ching Chuang *, Chi-Hung Liao *, Chien-Shiun Liao **

* Division of Chemical Engineering, Institute of Nuclear Energy Research

** Department of Chemical Engineering and Materials Science, Yuan Ze University

ABSTRACT

The metal ferrocyanide granular inorganic adsorbent based on phosphate geopolymer for the removal of Cs in either batch or packed-bed operation has been developed in this study. The adsorbent was synthesized from the acid-base reaction between metal ferrocyanide and acidic phosphate at room temperature. In this work, the compressive strength of granular inorganic adsorbent was investigated under different liquid-to-solid, metal ferrocyanide-to-geopolymer and MgO-to-KH₂PO₄ ratios. The result showed that the compressive strength of the adsorbent increased with the increase of MgO-to-KH₂PO₄ ratio. On the other hand, the increase of metal ferrocyanide-to-geopolymer ratio or liquid-to-solid ratio lowered the compressive strength of the adsorbent. It was found that the optimization of liquid-to-solid, metal ferrocyanide-to-geopolymer and MgO-to-KH₂PO₄ ratios was important in improving both the compressive strength and the adsorption capacity of the adsorbent. In this study, the synthesized granular inorganic adsorbent has demonstrated a Cs removal efficiency of over 99% and an adsorption capacity of 1.1-1.3 meq/g in simulation wastewater containing 2000 ppm Cs under adsorbent dose of 0.0067 g/ml.

INTRODUCTION

The release of cesium radionuclide into the environment is of concern due to its high solubility characteristics when up-taken by human body through food chain. Moreover, the long half-life of ¹³⁷Cs (30 years) has made it a highly radiotoxic nuclide. Therefore, removal of cesium radionuclide in wastewater from Nuclear Power Plant (NPP) or nuclear facilities is an important issue for nuclear waste management. Nuclear waste effluents from NPP typically is acidic (i.e. HNO₃) and has high concentration of sodium (i.e. NaNO₃) [1]. Special attention has been given to the selective removal of ¹³⁷Cs from radioactive wastewater containing highly acidic and concentrated sodium. Furthermore, granules suitable for column operation have been prepared by binding or precipitating fine inorganic adsorbent onto porous particles. Among various types of granular inorganic adsorbent, the ferrocyanides of transition metals (II) (Ni, Cu, Zn, Fe and others) demonstrate the highest selectivity towards the removal of cesium from radioactive wastewater [2, 3]. Konecny et al. used porous silica gel particles as substrate to load K₄Fe(CN)₆ and then reacted with ZnSO₄ to form granular inorganic adsorbent[4]. Shabana et al. used granular porous polymethylmethacrylate as support and loaded with potassium iron(III) hexacyanoferrate(II) [5]. Hitoshi et al. loaded potassium nickel hexacyanoferrates on granular porous chabazite[6]. Hitoshi et al. reported the incorporation of potassium iron(III) hexacyanoferrate(II) crystal on the granular porous support of zeolite[7]. Although above mentioned granular porous support has good retention capacity for radioactive cesium, they have low mechanical stability and high flow resistance, leading to clogging of the column. In addition, the preparation procedures were complicated and the product was often not reproducible. In order to improve their low mechanical stability and high flow resistance, the fine metal ferrocyanides have been produced by incorporation with some organic binder. Rao et al. used polyvinyl acetate as binder in the preparation of copper(II) ferrocyanide on polyurethane foam support[8]. Someda et al. prepared transition metal ferrocyanides on polyacrylonitrile as binder and support[9]. Even though granular adsorbent within organic binder has good mechanical stability, it might be

degraded by radiation and other biological action overtime, resulting in the leakage of radioactive cesium nuclides. In order to overcome the low mechanical stability and high flow resistance of granular adsorbent and avoid using organic binder, we attempted to combine fine transition metal ferrocyanides powder with geopolymer. Geopolymer is often used for the stabilization/solidification (S/S) of mixed wastes as well as low-level nuclear waste due to its excellent mechanical strength [10-12]. Various types of geopolymer, silicate alkali-based geopolymer[13] and phosphoric acid-based geopolymer[14], have been developed during the last decade. It was reported that the high pH of silicate alkali-based geopolymers may induce the hydrolysis of transition metal ferrocyanides, leading to the destruction of its molecular structure [15]. On the other hand, in phosphoric acid-based geopolymer, the main reaction product is magnesium potassium phosphate hexahydrate or k-struvite ($\text{MgKPO}_4 \cdot 6\text{H}_2\text{O}$)[16], which is formed by the acid-based reaction between burned magnesia and potassium dihydrogen phosphate[11]. In this case, hydrolysis of transition metal ferrocyanides can be avoided. The present study deals with the preparation of zinc ferrocyanide-loaded k-struvite, characterization of this granular inorganic adsorbent, and its uptake property towards ^{137}Cs in simulated wastewater.

Materials and Methods

Material

Potassium ferrocyanide trihydrate ($\text{K}_4[\text{Fe}(\text{CN})_6] \cdot 3\text{H}_2\text{O}$) and zinc sulfate heptahydrate ($\text{ZnSO}_4 \cdot 7\text{H}_2\text{O}$) were used as received for the preparation of zinc ferrocyanide powder[17]. Sintered magnesium oxide (MgO), potassium hydrogen phosphate (KH_2PO_4) and boric acid were used as received for the preparation of phosphoric acid-based geopolymer which then mixed with KZnFC[18]. DT-30A (commercial granular inorganic adsorbent, Diversified Technologies Services, Inc.) was used for comparison in terms of distribution coefficient, adsorption capacity and compressive strength.

Preparation of Potassium Zinc Ferrocyanide Powder (KZnFC) [17]

The KZ41, KZ21, KZ11, KZ12 and KZ14 were designated for the prepared KZnFC with $\text{K}_4[\text{Fe}(\text{CN})_6] \cdot 3\text{H}_2\text{O}$ (1M)-to- $\text{ZnSO}_4 \cdot 7\text{H}_2\text{O}$ (1M) volume ratio of 4:1, 2:1, 1:1, 1:2 and 1:4, respectively. For instance, the preparation of KZ41 is as follows. 73.67 g of $\text{K}_4[\text{Fe}(\text{CN})_6] \cdot 3\text{H}_2\text{O}$ (1 M), and 14.378 g of $\text{ZnSO}_4 \cdot 7\text{H}_2\text{O}$ (1M) were added into 200 ml, and 50 ml of deionized water, respectively. Then, $\text{K}_4[\text{Fe}(\text{CN})_6] \cdot 3\text{H}_2\text{O}$ solution was added into $\text{ZnSO}_4 \cdot 7\text{H}_2\text{O}$ solution dropwisely followed by stirring for 7 days at room temperature to form white slurry. Finally, the resulting slurry was washed by deionized water followed by centrifuge and dried in vacuum at 80°C for 2 h to obtain KZ41. Similar method was used to obtain KZ21, KZ11, KZ12 and KZ14.

Preparation of Phosphoric Acid-Based Geopolymer for Granulation of KZnFC

Adjustment of MgO-to-KH₂PO₄ Mass Ratio

The MK11, MK21, MK31, MK41 and MK51 were designated for the prepared KZnFC granules via phosphoric acid-based geopolymer with MgO-to- KH_2PO_4 mass ratio of 1:1, 2:1, 3:1, 4:1 and 5:1, respectively. For instance, the preparation procedure for MK51 is as follows. 8.23 g of MgO, 1.65 g of KH_2PO_4 , 10 g of KZnFC and 0.12 g of Boric acid were first mixed by milling for 2 hr. Then, 12 ml of de-ionized water was added slowly into the premixed power while stirring. Stirring of the slurry was kept for 5 min and then it was poured into a mold for hardening. After hardening, compressive strength of the bulk was measured. To test the removal efficiency for Cs, the solidified KZnFC bulk was crushed and sieved to obtain granular KZnFC adsorbent with particle size of 1-2 mm. Prior to adsorption test, the granular KZnFC adsorbents were washed to remove fine powder by deionized water and dried at 60°C for 24 hr. Similar method was used to

obtain MK21, MK31, MK41 and MK51.

Adjustment of KZnFC-to-Geopolymer Mass Ratio

The KC11, KC21, KC41 and KC61 were designated for the prepared KZnFC granules with KZnFC-to-geopolymer mass ratio of 1:1, 1.2:1, 1.4:1 and 1.6:1, respectively. For instance, the preparation procedure for K11 is as follows. 9.88 g of geopolymer (containing MgO and KH_2PO_4 with mass ratio of 2:1 or 3:1), 10 g of KZnFC and 0.12 g of Boric acid were first mixed by milling for 2 hr. Then, 12 ml of de-ionized water was added into the premixed power while stirring. Stirring of the slurry was kept for 5 min and then it was poured into a mold for hardening. After hardening, compressive strength of the bulk was measured. To test the removal efficiency for Cs, the solidified KZnFC bulk was crushed and sieved to obtain granular KZnFC adsorbent with particle size of 1-2 mm. Prior to adsorption test, the granular KZnFC adsorbents were washed to removed fine powder by deionized water and dried at 60 °C for 24 hr. Similar method was used to obtain KC21, KC41 and KC61.

Characterization

Material Properties

X-ray diffraction (XRD) spectra were obtained on a D8 ADVANCE using Cu K_α radiation (45 kV and 40 mA). The compressive strength of the samples was measured using a mechanical tester (HT-2402) with granular adsorbent particle size of around $\psi 6 \times 11$ mm. At least 10 sample were tested in the mechanical test with loading speed is 20 mm/min.

2.4.2 Batch Adsorption Test for the Prepared Adsorbents

The adsorption capacity of adsorbent was calculated as

$$Q(\text{meq/g, mole/g}) = \frac{(C_0 - C) \times V}{M \times W} \quad (1)$$

Where C_0 is initial cesium concentration (ppm), C is the final cesium concentration (ppm) in the solution, V is the volume of simulated solution (L), M is the cesium molecular weight (g/mole), W is the weight of adsorbent (g).

The cesium removal efficiency (R , %) of adsorbent in the simulated solution was determined as [19]

$$R(\%) = \frac{(C_0 - C) \times 100}{C_0} \quad (2)$$

where C_0 is initial cesium concentration (ppm), C is the final cesium concentration (ppm) in the solution, V is the volume of simulated solution (mL), W is the weight of adsorbent (g).

To perform the adsorption test, 0.2g of powder KZnFC or granular adsorbent was added to the simulated cesium ion solution (2000 ppm, 30 ml, CsNO_3 , 0.0067 g/ml). The mixture solution was shaken on a rotary shaker at 25°C for 24hr. When the adsorption test was completed, the mixture solution was centrifuged at 4000 rpm for 30 min. The supernatant liquid was measured by atomic absorption spectrometer (iCE 3300) to determine the residual cesium ion concentration. In addition, short-term adsorption tests were performed for the prepared adsorbents. Here, 0.2g of powder KZnFC or granular adsorbent was added to the simulated cesium ion solution (2000 ppm, 30 ml, CsNO_3). The mixture solution was shaken on a rotary shaker at 25°C for 2 min, 5 min, 10 min, 30 min, 60min, and 120 min.

Results and Discussion
Potassium Zinc Ferrocyanide Powder (KZnFC)

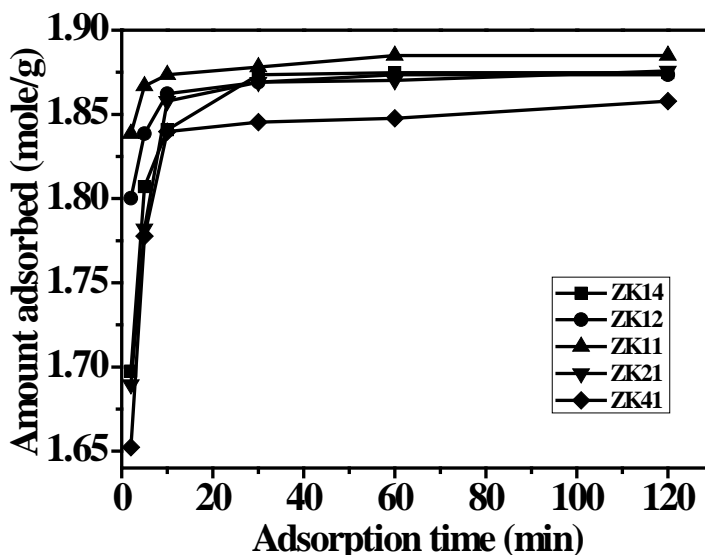


Fig. 1 Time-dependent cesium uptake (mole/g) for powder KZnFC

Fig. 1 shows the time-dependent cesium uptake (mole/g) for various powder KZnFCs. The result shows that the amount of adsorbed cesium ion approached equilibrium within 2 hr for all adsorbents. Among them, ZK11 shows the highest cesium uptake, suggesting that too high or too low $K_4[Fe(CN)_6] \cdot 3H_2O$ -to- $ZnSO_4 \cdot 7H_2O$ ratio may not benefit the cesium uptake of the adsorbents. It was reported that the high $K_4[Fe(CN)_6] \cdot 3H_2O$ -to- $ZnSO_4 \cdot 7H_2O$ ratio is favorable to give a high yield of $K_2Zn_3[Fe(CN)_6]_2$ [2] and the cesium uptake of $K_2Zn_3[Fe(CN)_6]_2$ is higher than that of $Zn_2Fe(CN)_6$ [20], attributing to the improved the ion exchange rate of the cesium ion with the potassium ion [17]. In contrary, excess $K_4[Fe(CN)_6] \cdot 3H_2O$ -to- $ZnSO_4 \cdot 7H_2O$ mole ratio will leave excess potassium ions in solution which may restrict the ion exchange of cesium ion by $K_2Zn_3[Fe(CN)_6]_2$ [21]. The above-mentioned result shows that ZK11 has higher uptake of cesium among the adsorbents tested, especially in a short period of adsorption time, meaning it requires less residence time when applies in the column. In addition, ZK11 exhibits an adsorption capacity of 1.88 meq/g, which is higher than that of the commercial adsorbent, DT-30A, (1.5 meq/g) for an adsorption time of 2 hr. Therefore, ZK11 was selected for the granulation of KZnFC via phosphoric acid-based geopolymer.

Effect of MgO-to-KH₂PO₄ Mass Ratio for the Preparation of Granular KZnFC Adsorbents Compressive Strength

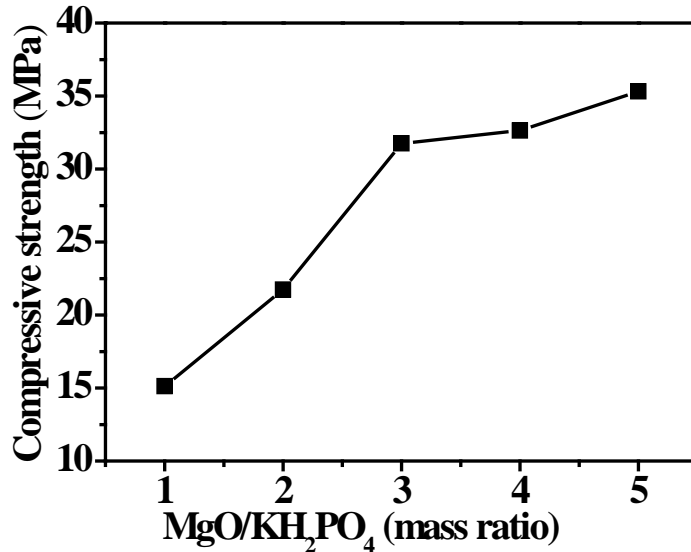


Fig. 2 Compressive strength of the geopolymer with different MgO-to-KH₂PO₄ mass ratios

The mechanism of phosphoric acid-based geopolymer formation involves Mg²⁺, K⁺ and PO₃⁻⁴ existed in the solution at the specific value of pH according to the Eq. (4)[11, 22]:



First, KH₂PO₄ was dissolved by the added water to release H⁺, which initializes the hydration reaction. Then, MgO begins to dissolve, increasing the pH value of the mixture. When the pH value is over 7, MgKPO₄·6H₂O is formed. Fig. 2 shows the compressive strength of the geopolymer with different MgO-to-KH₂PO₄ mass ratios. It is found that the compressive strength of geopolymer increases with the increase of MgO-to-KH₂PO₄ mass ratios. The largest compressive strength value was about 35.32 MPa for MK51 with the MgO-to-KH₂PO₄ mass ratios of 5:1. This may be due to that fact that the geopolymer of MK51 not only composed of the hydrated product, but also excess residual MgO particle. Such residual MgO particles may improve the compressive strength of the geopolymer. It was reported that the higher MgO content may brought much more internal stress in sample lead to fast setting [23].

XRD Diffraction Patterns

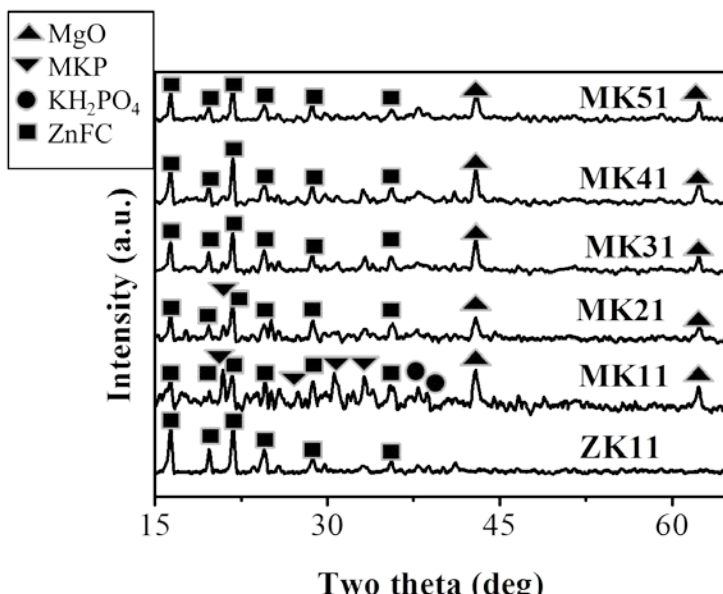


Fig. 3 XRD diffraction patterns of granular KZnFC adsorbents with different MgO-to-KH₂PO₄ mass ratios

The increase of compressive strength with increase of MgO-to-KH₂PO₄ mass ratios can also be explained by the XRD patterns of the samples as shown in Fig. 3. The diffraction peaks of KH₂PO₄, MgO, KZnFC (KZ11) and MgKPO₄·6H₂O (MKP) are noted for MK11 with the MgO-to-KH₂PO₄ mass ratios of 1:1. The intensity of the diffraction peak representing KH₂PO₄ decreases with the increase of the MgO-to-KH₂PO₄ mass ratios, suggesting that the crystallinity of MgKPO₄·6H₂O was affected by the content of MgO. This is mainly attributed to the pH-dependent nature of the nucleation and growth of hydrated product [23]. For the case of the MK51, the excess amount of MgO added results in a rapid increase of pH value, leading increase in the nucleation rate. Since there was not enough time for the precipitated MgKPO₄·6H₂O to crystallize, amorphous phase was observed for MK51. On the other hand, in the case of MK11, the pH value increased slowly, providing enough time for the precipitated MgKPO₄·6H₂O to crystallize [23]. Therefore, with the increase of the MgO-to-KH₂PO₄ mass ratios, the amount of crystallized phase decreased while the amount of amorphous phase increased.

Adsorption Capacity

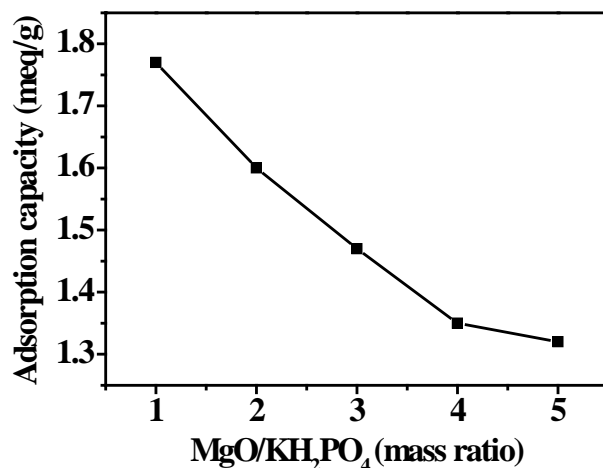


Fig. 4 Adsorption capacity of granular KZnFc adsorbents with different MgO-to-KH₂PO₄ mass ratios

The effect of MgO-to-KH₂PO₄ mass ratios on Cs ion adsorption is shown in Fig. 4. The maximum adsorption capacity for MK11, MK21, MK31, MK41 and MK51 is 1.77, 1.6, 1.47, 1.35, and 1.32 meq/g, respectively. The adsorption capacity was increased with the decrease of MgO-to-KH₂PO₄ mass ratios. In contrast, the compressive strength was increased with the increase of MgO-to-KH₂PO₄ mass ratios as result of more compact granular inorganic adsorbents formed. Yue et al.[24] reported that high adsorption capacity have been achieved resulting from the rigidly open pore structure and extremely high surface area of the immobilization of copper ferrocyanide on granular porous ceramic support, which suggests that the more compact the granular inorganic adsorbent was, the less porous the granular inorganic adsorbent was. Therefore, the internal surface area of K₂Zn₃[Fe(CN)₆]₂ (ZK11) may not be as high as that of MK51, resulting in low adsorption capacity. To optimize both the mechanical stability and the adsorption capacity, MK21 and MK31 were selected to run the subsequent tests.

Effect of KZnFc-to-Geopolymer Mass Ratio for the Prepared Granular KZnFC Adsorbents Adsorption Capacity and Compressive Strength

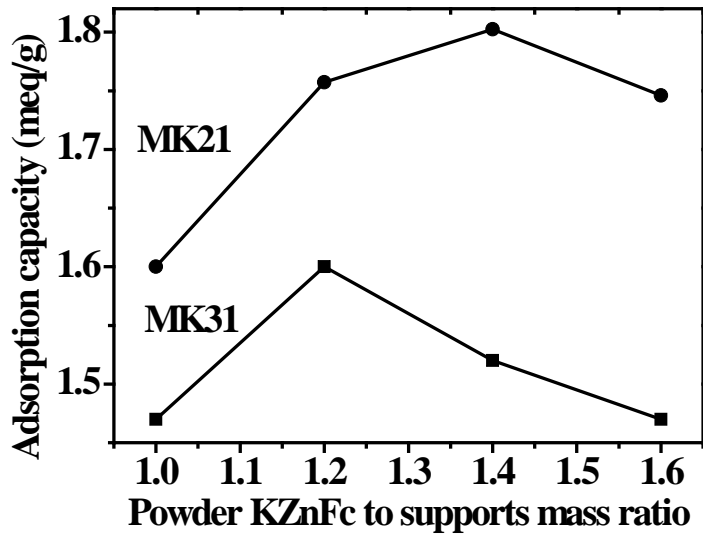


Fig. 5 Adsorption capacity of granular KZnFC adsorbents with different KZnFc-to-geopolymer mass ratios

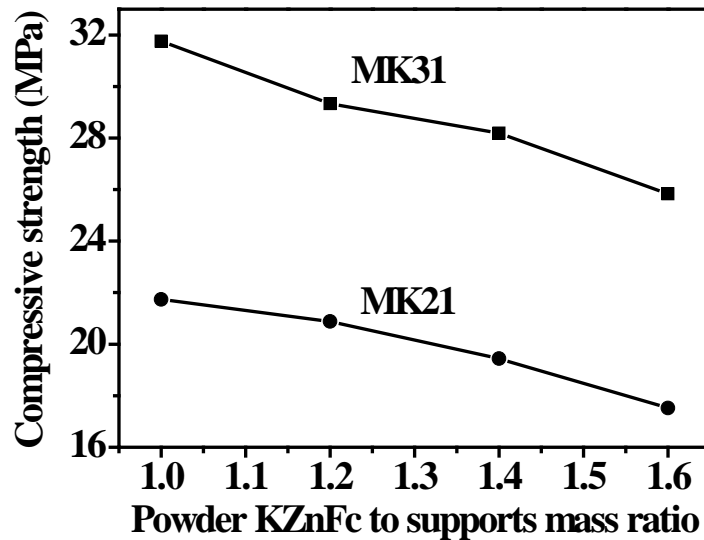


Fig. 6 Compressive strength of the bulk with different KZnFc-to-geopolymer mass ratios

In order to improve the adsorption efficiency of MK21 and MK31, KZnFc content was increased for the preparation of granular inorganic adsorbents. Fig. 5 shows results of the adsorption experiment. The amount of adsorbed cesium ions for MK21 increases with the increase of KZnFc-to-geopolymer mass ratios, reaching a maximum at the mass ratio of 1.4. On the other hand, the maximum adsorption for MK31 is at the KZnFc-to-geopolymer ratio of 1.2. The drop of adsorption capacity may be due to the excess KZnFc blocking the pore sites of the granular adsorbents, leading to decrease in contacting surface area with the solution. Since MK21 may have more pore sites than MK31, more KZnFc can be loaded on MK21 than on MK31, leading to

higher adsorption capacity of MK21-KC41 (1.8 meq/g) than MK31-KC21 (1.6 meq/g). Fig. 6 shows the compressive strength of granular KZnFC adsorbents with different KZnFcto-geopolymer mass ratios. It can be seen that the compressive strength of MK31 and MK21 decreased with the increase of KZnFcto-geopolymer mass ratios. Since geopolymer is a hardening agent, reduce its content may decrease the compressive strength.

Effect of Contacting Time on Cs Absorption under Various Cs Concentrations

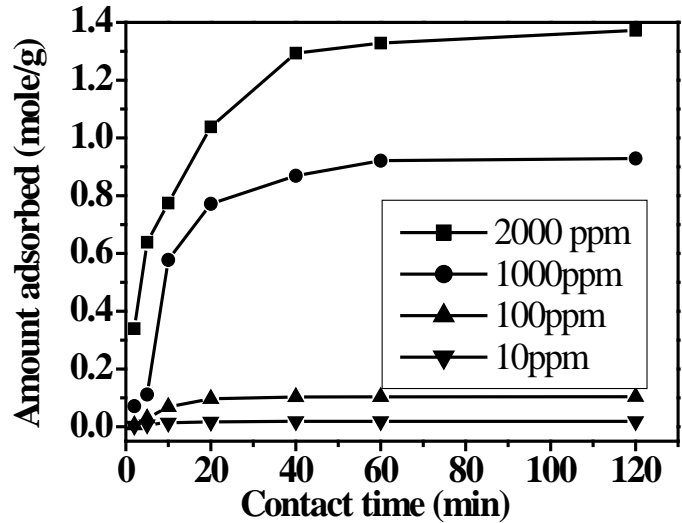


Fig. 7 Time-dependent adsorption of cesium on MK21-KC41 under various Cs concentrations

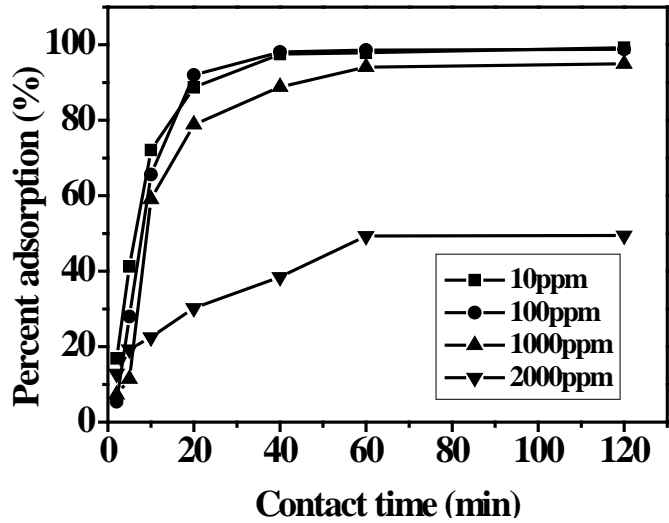


Fig. 8 Time-dependent cesium adsorption efficiency on MK21-KC41 under various Cs concentrations

The adsorption of cesium ion on MK21-KC41 granular inorganic adsorbents was examined at different concentrations of Cs (10ppm, 100ppm, 1000ppm, 2000ppm) as a function of contacting

time at room temperature as shown in Fig 5. With the increase of the contacting time, the cesium ion uptake increased and remained constant after the equilibration time of 60 min. The amount adsorbed at equilibrium increases from $1.86 \cdot 10^{-2}$ to 1.37 (mole/g) with the increase in concentration over the range 10 to 2000 ppm. However, the percentage of cesium ion adsorption increased from 49.5 to 99.28 % with the decrease of initial concentration in the range from 2000 to 10 ppm. The result suggests that the availability of larger sorbent surface sites for a relatively smaller number cesium ions at low initial concentration. The smooth and continuous curves reveal that uptake is initially fast, becoming slower later on and ultimately reaches saturation. Furthermore, the cesium ions preferentially occupy many of active sites of MK21-KC41 in a random manner results in the rapid adsorption rate initially. As time went by, the rate of uptake became slower and eventually reached a constant value due to the saturation of the adsorption surface.

Adsorption Isotherms

The distribution of metal ions between the liquid phase and solid phase can be described by mathematical model equation such as the Langmuir and Freundlich isotherm models. This relates adsorption capacity (q_e) to the equilibrium adsorbate concentration (C_e) in the bulk fluid phase.

Langmuir Adsorption Isotherm

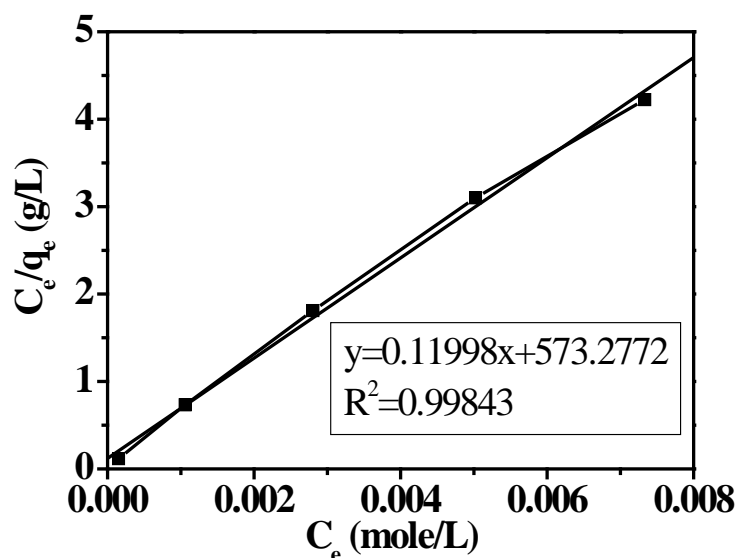


Fig. 9 Langmuir adsorption isothermal or cesium ions adsorption on the MK21-KC41

The Langmuir adsorption isothermal is the simplest theoretical model for monolayer adsorption with constant heat of adsorption for all sites and without interaction between adsorbed molecules. It suggests a finite number of identical surface sites on the surface of adsorbents. In addition, the model assumes uniform energies of adsorption onto the surface and no transmigration of the adsorbate. The Langmuir isotherm is represented by the following equation: [25]

$$\frac{C_e}{q_e} = \frac{1}{Q_0 b} + \frac{C_e}{Q_0} \quad (5)$$

where C_e is the equilibrium concentration (mole/L), q_e is the amount of the cesium ion adsorbed at equilibrium (mole/g) and Q_0 and b are Langmuir constants relate to the adsorption

capacity and the energy of adsorption, respectively. The plots of C_e/q_e vs. C_e are found to be linear which indicate that the adsorption of cesium ion follows the Langmuir adsorption isotherm model. Therefore, taking experimental data of different weigh adsorbent with fixed initial concentration result in different adsorptive equilibrium concentration into the Langmuir adsorption equation for isothermal were shown in Fig. 9. Q_0 and b were calculated from the slope and intercept of the plots and were found to be 8.33, 2.09E-4, respectively.

The essential characteristics of a Langmuir isotherm could be described in the terms of a dimensionless constant separation factor or equilibrium R_L which is defined by[26]

$$R_L = \frac{1}{1 + bC_0} \quad (6)$$

where, C_0 is the initial cesium ion concentration (mol/L) and b is the Langmuir constant related to the energy of adsorption. The R_L values at different concentrations are list in Table 1. Taking the energy of adsorption constant b data into equilibrium R_L could be evaluated (0.99). The R_L value ($0 < R_L < 1$) indicated that the adsorption of cesium ion by MK21-KC41 is favorable.

R_L value	Type of isotherm
$R_L > 1$	unfavourable
$R_L = 1$	Linear
$0 < R_L < 1$	Favourable
$R_L = 0$	Irreversible

Freunchlich adsorption isotherm

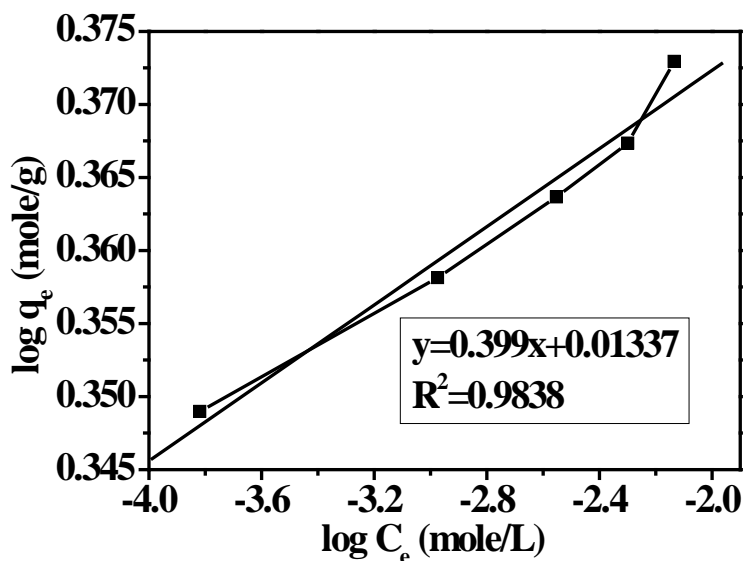


Fig. 10 Freunchlich adsorption isothermal or cesium ions adsorption on the MK21-KC41

The Freundlich equation is used for heterogeneous surface energies from the presence of different functional groups on the surface, and the various adsorbent – adsorbate interactions. In contrast to the Langmuir equation, the Freundlich isotherm assumes sorption onto sorbent surfaces, which

are characterized by heterogeneous sorption sites. It also assumes that the stronger adsorption sites are occupied first and the binding strength decreases with increasing binding site occupation. The results of concentration-dependent cesium ions adsorption on MK21-KC41 were analyzed by applying the Freundlich adsorption isotherm [27] in its logarithmic form:

$$\log q_e = \log k + \frac{1}{n} \log C_e \quad (7)$$

where q_e is the amount of cesium ions adsorbed at equilibrium (mole/g), C_e is the adsorptive equilibrium concentration (mole/L). k and $1/n$ are Freundlich constants which correspond to adsorption capacity and adsorption intensity, respectively; n (g/L) is a measure of the deviation from the linearity of adsorption. This value indicates the degree of non-linearity between the solution concentration and adsorption as follows: if $n = 1$, the adsorption is linear adsorption process; if $n < 1$, adsorption is an unfavourable adsorption process; and if $n > 1$, adsorption is a favourable adsorption process.

The plot of $\log q_e$ vs. $\log C_e$ was found to be linear which suggests that the adsorption of cesium ions on MK21-KC41 obeyed Freundlich adsorption isotherm over the entire range of adsorptive concentration studied. Therefore, taking experimental data of different weight adsorbent with fixed initial concentration result in different adsorptive equilibrium concentration into the Freundlich adsorption equation for isothermal were shown in Fig. 10. The $1/n$ and $\log k$ were founded from the slope and intercept of the plots to be 0.399, 0.01337, respectively. The inverse of adsorption intensity was evaluated and the result was greater than one (2.5). The result suggests that surface of the adsorbent was heterogeneous in nature with an exponential distribution of active sites [28]

CONCLUSION

Preparation of granular KZnFC via phosphoric acid-based geopolymer was carried out in this study. The granular KZnFC with the largest compressive strength value was MK51 (35.32 MPa). The improved compressive strength was due to the excess residual MgO particles. However, MK51 exhibits the lowest adsorption capacity (1.32 meq/g) due to its lowered porous structure. To optimize both the adsorption capacity and the mechanical stability, only MK21 (1.47 meq/g) and MK31 (1.35 meq/g) were selected to run column operations. The performances of both granular KZnFCs were comparable to that of commercial granular inorganic adsorbent (DT-30A, 1.45 meq/g). To improve the adsorption efficiency of MK21 and MK31, KZnFc content was increased. However, excess KZnFc content did not benefit granular KZnFC's adsorption efficiency due to the limited pore sites on the adsorbent. As a result, the optimal KZnFC-to-geopolymer ratio in achieving maximum adsorption capacity was 1.4 for MK21-KC41, and 1.2 for MK31-KC21. In addition, the adsorption of cesium ion for MK21-KC41 with various contacting time was examined at different concentrations of Cs (10 ppm, 100 ppm, 1000 ppm, 2000 ppm). The adsorption efficiency remained constant after the equilibration time of 60 min. Moreover, the adsorption behavior of cesium ion on MK21-KC41 can be described by both the Langmuir adsorption equation and the Freundlich adsorption equation.

REFERENCES

- [1] T. A. Todd, K. N. Brewer, D. J. Wood, P. A. Tullock, N. R. Mann, and L. G. Olson, "Evaluation and Testing of Inorganic Ion Exchange Sorbents for the Removal of Cesium-137 from Actual Idaho Nuclear Technology and Engineering Center Acidic Tank Waste," *Separation Science and Technology*, vol. 36, pp. 999-1016, 2001.
- [2] C. Loos-Neskovic, "Zinc and nickel ferrocyanides: preparation, composition and structure," *Talanta*, vol. 31, pp. 1133-1147, 1984.
- [3] R. Harjula, J. Lehto, E. H. Tusa, and A. Paavola, "Industrial scale removal of cesium with hexacyanoferrate exchanger—process development," *Nuclear technology*, vol. 107, pp. 272-278, 1994.
- [4] C. Konecny and R. Caletka, "Adsorption properties of insoluble hexacyanoferrates(II) supported on silica gel," *J. Radioanal. Chem*, vol. 14, pp. 255-266, 1973.
- [5] S. Taj, D. Muhammad, M. A. Chaudhry, and M. Mazhar, "Lithium, rubidium and cesium ion removal using potassium iron(III) hexacyanoferrate(II) supported on polymethylmethacrylate," *Journal of Radioanalytical and Nuclear Chemistry*, vol. 288, pp. 79-88, 2010.
- [6] H. Mimura, M. Kimura, K. Akiba, and Y. Onodera, "Selective Removal of Cesium from Sodium Nitrate Solutions by Potassium Nickel Hexacyanoferrate-Loaded Chabazites," *Separation Science and Technology*, vol. 34, pp. 17-28, 1999.
- [7] H. Mimura, M. Kimura, K. Akiba, and Y. Onodera, "Separation of Cesium and Strontium by Potassium Nickel," *Journal of Nuclear Science and Technology*, vol. 36, pp. 307-310, 1999.
- [8] S. V. S. Rao, K. B. Lal, S. V. Narasimhan, and J. Ahmed, "Copper ferrocyanide — polyurethane foam as a composite ion exchanger for removal of radioactive cesium," *Journal of Radioanalytical and Nuclear Chemistry*, vol. 240, pp. 269-276, 1999.
- [9] H. H. Someda, A. A. ElZahhar, M. K. Shehata, and H. A. El-Naggar, "Supporting of some ferrocyanides on polyacrylonitrile (PAN) binding polymer and their application for cesium treatment," *Separation and Purification Technology*, vol. 29, pp. 53-61, 2002.
- [10] A. S. Wagh, S.-Y. Jeong, and D. Singh, "High strength phosphate cement using industrial byproduct ashes," in *Proc. First Intl. Conf. on High Strength Concrete*, eds. A. Azizinamini, D. Darwin, and C. French), *Am. Soc. Civil Eng*, 1997, pp. 542-553.
- [11] D. Singh, V. R. Mandalika, S. J. Parulekar, and A. S. Wagh, "Magnesium potassium phosphate

- ceramic for ^{99}Tc immobilization," *Journal of Nuclear Materials*, vol. 348, pp. 272-282, 2006.
- [12]J. Torras, I. Buj, M. Rovira, and J. de Pablo, "Semi-dynamic leaching tests of nickel containing wastes stabilized/solidified with magnesium potassium phosphate cements," *Journal of hazardous materials*, vol. 186, pp. 1954-1960, 2011.
- [13]J. Davidovits, "Properties of geopolymer cements," in *First international conference on alkaline cements and concretes*, 1994, pp. 131-149.
- [14]L.-p. Liu, X.-m. Cui, Y. He, S.-d. Liu, and S.-y. Gong, "The phase evolution of phosphoric acid-based geopolymers at elevated temperatures," *Materials Letters*, vol. 66, pp. 10-12, 2012.
- [15]S. J. Robuck and R. G. Luthy, "Destruction of iron-complexed cyanide by alkaline hydrolysis," *Water Science & Technology*, vol. 21, pp. 547-558, 1989.
- [16]A. Wagh, D. Singh, S. Jeong, and R. Strain, "Ceramicrete stabilization of low-level mixed wastes-a complete story," Argonne National Lab., IL (United States). Funding organisation: USDOE Office of Environmental Restoration and Waste Management, Washington, DC (United States)1997.
- [17]S. Vlasselaer, W. D'Olieslager, and M. D'Hont, "Caesium ion exchange equilibrium on potassium-zinc-hexacyanoferrate(II) $\text{K}_2\text{Zn}_3(\text{Fe}(\text{CN})_6)_2$," *Journal of Inorganic and Nuclear Chemistry*, vol. 38, pp. 327-330, 1976.
- [18]A. J. Wang, Z. L. Yuan, J. Zhang, L. T. Liu, J. M. Li, and Z. Liu, "Effect of raw material ratios on the compressive strength of magnesium potassium phosphate chemically bonded ceramics," *Mater Sci Eng C Mater Biol Appl*, vol. 33, pp. 5058-63, Dec 1 2013.
- [19]H. Mimura, J. Lehto, and R. Harjula, "Selective Removal of Cesium from Simulated High-level Liquid Wastes by Insoluble Ferrocyanides," *Journal of Nuclear Science and Technology*, vol. 34, pp. 607-609, 1997.
- [20]C. Loos-Neskovic, M. Fedoroff, and M. O. Mecherri, "Ion fixation kinetics and column performance of nickel and zinc hexacyanoferrates(II)," *The Analyst*, vol. 115, p. 981, 1990.
- [21]B. Li, J. Liao, J. Wu, D. Zhang, J. Zhao, Y. Yang, *et al.*, "Removal of radioactive cesium from solutions by zinc ferrocyanide," *Nuclear Science and Techniques*, vol. 19, pp. 88-92, 2008.
- [22]I. Buj, J. Torras, D. Casellas, M. Rovira, and J. de Pablo, "Effect of heavy metals and water content on the strength of magnesium phosphate cements," *J Hazard Mater*, vol. 170, pp. 345-50, Oct 15 2009.
- [23]Z. Ding, *Research of magnesium phosphosilicate cement*, 2005.
- [24]Y. Lin, G. E. Fryxell, H. Wu, and M. Engelhard, "Selective Sorption of Cesium Using Self-Assembled Monolayers on Mesoporous Supports," *Environmental Science & Technology*, vol. 35, pp. 3962-3966, 2001.
- [25]I. Langmuir, "The Adsorption of Gases on Plane Surfaces of Glass, Mica and Platinum," *Journal of the American Chemical Society*, vol. 40, pp. 1361-1403, 1918.
- [26]K. R. Hall, L. C. Eagleton, A. Acrivos, and T. Vermeulen, "Pore- and Solid-Diffusion Kinetics in Fixed-Bed Adsorption under Constant-Pattern Conditions," *Industrial & Engineering Chemistry Fundamentals*, vol. 5, pp. 212-223, 1966.
- [27]H. M. F. Freundlich, "Over the adsorption in solution," *The Journal of Physical Chemistry*, vol. 57, pp. 385-470, 1906.
- [28]R. Sips, "On the Structure of a Catalyst Surface," *The Journal of Chemical Physics*, vol. 16, p. 490, 1948.