

## **THERMAL ASSAULT AND POLYURETHANE FOAM – EVALUATING PROTECTIVE MECHANISMS FOR TRANSPORT CONTAINERS<sup>i</sup>**

C.L. Williamson, Z.L. Iams  
General Plastics Manufacturing Company,  
Tacoma, WA, USA

### **ABSTRACT**

Rigid polyurethane foam used as Over-pack in transport containers, utilizes a variety of mechanisms to mitigate the thermal assault of a “regulatory burn.” Polymer-specific heat and foam k-factor are of limited usefulness in predicting payload protection. Properly formulated rigid polyurethane foam, as a consequence of its pyrolysis can provide additional safeguards. These ablative mechanisms are effective even when the foam has been crushed or fractured as a result of trauma. The dissociative transitions from polymer to gas and char, and the resulting gas-transport of heat from inside the package out into the environment, are efficient thermal mitigators. Also important is the in-situ production of an intumescent, insulative, carbonaceous char that confers thermal protection even when a package’s outer steel skin has been breached.

In our test program, 19 liter (Five gallon) steel pails were filled with protective foams and then exposed on one face to the flame of an “Oil Burner” as described in the US Federal Aviation Administration (FAA) “Aircraft Materials Fire Test Handbook”. When burning #2 diesel at a nominal rate of 18.5 pounds (8.39 kg)/hr, the burner generates a dirty, high emissivity flame that impinges the pail face with the thermal intensity of a full-scale pool-fire environment. Results of these tests, along with Thermo Gravimetric Analysis (TGA) and Differential Scanning Calorimetry (DSC) analysis on the subject foams are reported, and their relevance to full size packages and pool-fires are discussed.

### **INTRODUCTION**

Packaging design for the safe transport of nuclear materials would be far simpler if thermal protection was the only requirement. There are many insulative inorganic materials adequate for this purpose. However, transportation packages are also called upon to protect their “payloads” from kinetic accidents<sup>1</sup> (and in today’s world even explosive blasts<sup>2</sup>) before thermal exposure. Hence the package must first preclude inadvertent release resulting from loss of containment and preserve package insulative integrity for subsequent fire blocking.

General Plastics has installed rigid polyurethane foam in transportation over-packs and impact limiters for this dual purpose since 1971. Foam Impact energy absorption is reasonably well understood, but deep insight into its thermal protective mechanisms has remained elusive. Whether or not a package survives an IAEA fire<sup>3</sup> depends upon many variables, including those of both package design and materials. Our research objective was to isolate and quantify foam properties in order to provide enhanced protective characteristics.

## **POSSIBLE FOAM THERMAL PROTECTIVE MECHANISMS**

To begin, we hypothesized likely mechanisms for the thermal protection imparted by LAST-A-FOAM® FR-3700 series rigid polyurethane foams.<sup>4</sup> These mechanisms are both physical and chemical and result from foam characteristics including specific heat, thermal conductivity (k-factor) and ablative characteristics such as pyrolysis gas heat transfer, evolved combustion products, enthalpy of anoxic pyrolysis, conditions for char formation and char quality.

## **METHODOLOGY**

Though fires are notoriously difficult to scale, we sought to design a medium-scale test that would yield engineering data relevant to full size fires and packages. Regulatory fires impinge on all sides of a package, and of course the area/volume ratios and the payload thermal mass of designs vary greatly.

To better understand foam decomposition, we reviewed Thermogravimetric Analysis (TGA) on the foam both tested in air and Nitrogen, as well as Differential Scanning Calorimetry (DSC) tested in Nitrogen.

For our medium scale testing, we elected to utilize a two-dimension test methodology by subjecting only one surface of our test article to thermal assault. For pool fire representation, we chose the “Oil Burner”, as called out in commercial aircraft “Joint Airworthiness Regulations” FAR/JAR 25.853, which is used for testing the flammability of seating and the fire hardening of cargo wall liners. This burner is completely described in the US FAA’s “Fire Test Handbook”<sup>5</sup>. The 280 mm wide x 152 mm high burner exit cone, when adjusted to produce a ~1050°C temperature at a distance of 100 mm from the burner exit cone, results in a radiant heat flux of 19.6 W/cm<sup>2</sup> on our calorimeter<sup>6</sup>. This is somewhat higher than that for pool fire heat flux referenced<sup>7</sup> for Diesel, JP4 or Gasoline (Petrol) at 13.0 W/cm<sup>2</sup>, though less than that for Butane at 22.5, Propane at 25.0 or LNG at 26.5 W/cm<sup>2</sup>.


## **THERMAL ANALYSIS**

Differential Scanning Calorimetry (DSC) was performed on FR-3710 foam (10 lbs/ft<sup>3</sup> density before crushing) in an open pan, using a 50 cc/min N<sub>2</sub> purge. The high purge rate helped separate initial endotherm from the anoxic exotherm resulting from the later recombination of molecular fragments into lower energy oligomers. These oligomers “are transported into the gas phase, and sometimes referred to as tar.”<sup>8</sup> If vented (not condensing in cooler parts of an overpack) these.


In practice, the anoxic exotherm is not self-sustaining, and the FR-3710 foam self-extinguishes when the external heat flux ceases, and the unit cools.

TGA’s, Figures 1 and 2, were conducted on FR-3706 foam in both air and Nitrogen, disclosing the first (main) decomposition temperatures of 338 and 354 °C respectively. Most interesting is

that throughout the broad temperature range of approximately 340 through 650 °C, the weight remaining in air is greater than in N<sub>2</sub>- an indication that Oxygen significantly enhances char formation!

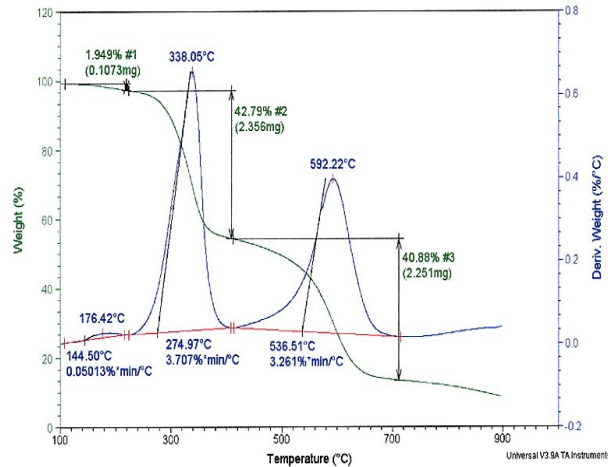

**Fig. 1. TGA FR-3706 in Air**

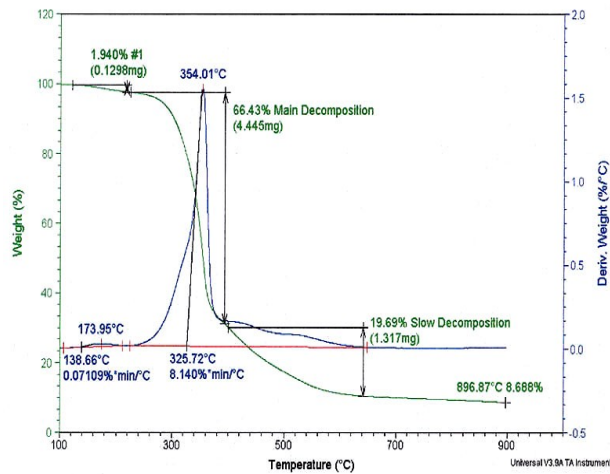


**Fig. 2. TGA of FR-3706 in Nitrogen**

## EFFECT OF DENSITY AND EXPOSURE TIME ON FOAM EFFECTIVENESS

Four, 19 liter (5 gal.) steel pails, ~30 cm in diameter (tapering to 28 cm diameter at the rear) x ~33 cm deep, were filled with different densities of FR-3700 rigid urethane foam. Nominal foam densities were 0.108, 0.174, 0.305 and 0.413 g/cm<sup>3</sup> (6.74, 10.86, 19.03, and 25.77 lbs/ft<sup>3</sup>). 3.18 mm thick, stainless steel lids were then welded onto the pails. Each lid was vented with a 23.8

mm hole in its center. Test pails were then positioned as shown in Figure 3, with the burner cone 100 mm from the lid.

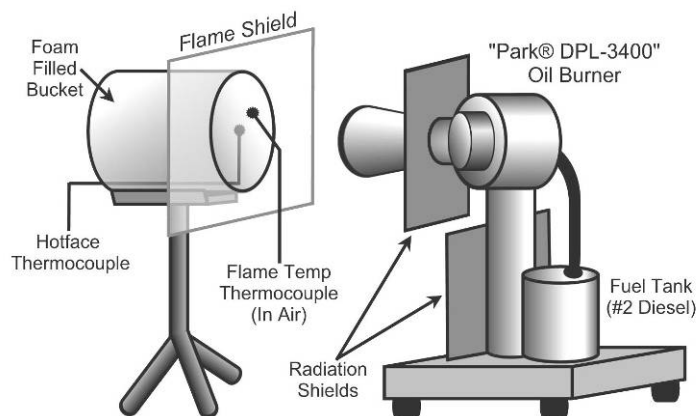

**Fig. 3. “Oil Burner” and test pail set-up**

When testing, the burner is turned on and the test pail lid exposed to the  $\sim 1080$  °C burner flame. Tests begin when the pail lid/hot-face temperature reaches  $801$  °C and ends 30 minutes later (though temperature recording continues until all thermocouples pass their peak temperatures). Hotface temperatures during tests average around  $950$  °C as determined using  $1.57$ mm, ungrounded, stainless-steel sheathed, type-k thermocouples in metal-to-metal contact with the rear of the hotface.

After the burner is turned off, the test pail is allowed to continue burning and then cool, while still positioned on the stand. The burn distance from the hotface is a readily discernible as a sharp transition between foam and char; this is as might be expected from the TGA curves (Figures 1 and 2). We know from the TGA that this transition is centered at  $354$  °C (in  $N_2$ ). At the end of the test, after all components have cooled, the pails are weighed, lids removed, char weighed and examined. The recession distance (burn distance) from the hot-face to the un-degraded foam is measured and recorded.

## TEST RESULTS

Table I shows the foam recession distance- the depth of foam consumed in a 30-minute regulatory exposure vs. the foam density. In all cases, varying amounts of carbonaceous char were found in the space where foam had been consumed. The regression line that can be calculated from the data in Table I indicates that foam effectiveness increases with increasing foam density- though at a decreasing rate. A  $0.10$  g/cm<sup>3</sup> density foam recesses about 10.7 cm. Doubling the foam density to  $0.20$  g/cm<sup>3</sup> does not cut the foam recession distance in half (to 5 cm). Rather, it reduces it by only 3.5 cm (a 7.2 cm recession distance). This relationship should be useful for package designers performing their initial calculations.

**Table I. Effects of foam Density on foam thermal effectiveness**

|   |                 |                  |                  |                  |
|---|-----------------|------------------|------------------|------------------|
| Density, g/cm <sup>3</sup><br>(lb/ft <sup>3</sup> ) | 0.108<br>(6.74) | 0.174<br>(10.86) | 0.305<br>(19.03) | 0.413<br>(25.77) |
| Initial Weight, g                                   | 5116            | 6576             | 9543             | 11228            |
| Final Weight, g                                     | 4690            | 5940             | 8799             | 10563            |
| Wt. Loss g  | 426             | 636              | 744              | 665              |
| Extinguish Time, minutes                            | 5:25            | 8:15             | 9:24             | 9:11             |
| Recession Distance, cm                              | 10.2            | 8.00             | 4.7              | 3.8              |

Table II illustrates the effect of exposure time on a single foam density. Six tests were conducted using six identical pails foamed with the same 0.181 g/cm<sup>3</sup> FR-3700 series foam. Exposure times were 5, 10, 15, 20, 25, and 31 minutes. Results calculated from Table II show that foam recession distance increases at a decreasing rate with respect to time.

**Table II. Recession Distance as a function of exposure time**

| Exposure Time, minutes                             | 5                | 10               | 15               | 20               | 25               | 31               |
|--|------------------|------------------|------------------|------------------|------------------|------------------|
| Density g/cm <sup>3</sup><br>(lb/ft <sup>3</sup> ) | 0.181<br>(11.29) | 0.181<br>(11.29) | 0.182<br>(11.36) | 0.182<br>(11.36) | 0.182<br>(11.36) | 0.182<br>(11.36) |
| Initial Weight, g                                  | 6655             | 6761             | 6778             | 6695             | 6649             | 6680             |
| Final Weight, g                                    | 6380             | 6382             | 6259             | 6082             | 5952             | 5945             |
| Wt. Loss, g  | 275              | 379              | 519              | 613              | 698              | 735              |
| Extinguish Time, minutes                           | 5:31             | 6:32             | 4:34             | 4:20             | 6:02             | 6:53             |
| Recession Distance, cm                             | 2.54             | 4.13             | 5.59             | 6.16             | 7.62             | 8.13             |

There is likely more than one mechanism at work. Firstly, as the foam recesses away from the hotface, heat flux to the un-degraded foam is reduced as the inverse-square of the recession distance, a minor effect at these distances. What we believe the regression illustrates most clearly is the insulative effect of carbonaceous char. As the un-degraded foam retreats, thicker char layer is able to mitigate more of the heat flux.

## EFFECT OF FOAM INTUMESCENCE

A fire impinging on a damaged container is a difficult scenario to model. Drop damage can penetrate or rip the outer metal skin. Additionally, impacted foam is likely to be cracked or crushed. To reproducibly simulate severely damaged foam (or other materials) we elected to test pails filled with randomly packed, 2.54 cm test cubes as shown in Figure 4. The packing fraction for randomly packed cubes with little orientational ordering, or registration between cubes, is about 0.582<sup>9</sup>. We discovered, that by just dropping foam cubes into an empty pail, and then spreading them out for lid installation, we achieved packing fractions in the range of 0.56 to 0.61, and with practice, the range could likely be reduced to between 0.58 and 0.60.



**Fig. 4. Random packed foam cubes**

By cutting three 46mm holes in the lower pail hot-face, and a similar vent hole at the upper rear of the pail (as oriented for testing) we create a chimney effect that pulls hot combustion gasses and outside air through the interstices between the foam cubes. These gas pathways simulate a damaged unit, where foam has been punctured and/or fractured. When tested in this manner, combustible organic materials lacking intumescent properties may exhibit difficulty self-extinguishing. Four test pails of randomly packed cubes were prepared:

- Tests-400519-1, 040521-1, and 04729-1 were conducted on standard and modified FR-3709 foams;
- Test-040728-1 with FR-3718 at a density of  $0.296 \text{ g/cm}^3$  was conducted as a direct comparison with Test 040630-1
- Test 040630-1 was conducted on GP's FR-10112, a rigid, Isocyanurate foam, Isocyanurate foam possess better high temperature performance than polyurethane, but lack intumescent properties.
- Test-040723-1 was conducted on uncoated, high density, ASTM C 208-95, Type-2 cane fiberboard.
- Test 041123-1 was conducted on nuclear grade Balsa wood.
- Test 041124-1 was conducted on nuclear grade Redwood

The results of these tests are shown in Table III

**Table III. Results from random cube experiment**

| Test Number  | 040519-1             | 040521-1             | 040729-1             | 040728-1         | 040630-1         | 040723-1         | 041123-1        | 041124-1         |
|--|----------------------|----------------------|----------------------|------------------|------------------|------------------|-----------------|------------------|
| Material   | FR-3709 <sub>1</sub> | FR-3709 <sub>2</sub> | FR-3709 <sub>3</sub> | FR-3718          | FR-10112         | Fiberboard       | Balsa           | Redwood          |
| Density, g/cm <sup>3</sup><br>(lb/ft <sup>3</sup> )          | 0.147<br>(9.17)      | 0.134<br>(8.36)      | 0.159<br>(9.92)      | 0.296<br>(18.47) | 0.187<br>(11.67) | 0.295<br>(18.41) | 0.146<br>(8.97) | 0.347<br>(21.69) |
| Packing Fraction   | 0.567                | 0.608                | 0.573                | 0.611            | 0.600            | 0.582            | 0.593           | 0.585            |
| Void, %  | 43.3                 | 39.2                 | 42.7                 | 38.9             | 40.0             | 41.8             | 46.8            | 41.5             |
| Effective Density g/cm <sup>3</sup><br>(lb/ft <sup>3</sup> ) | 0.083<br>(5.18)      | 0.082<br>(5.12)      | 0.091<br>(5.68)      | 0.181<br>(11.29) | 0.112<br>(6.99)  | 0.172<br>(10.73) | 0.078<br>(4.77) | 0.203<br>(12.69) |
| Initial Weight, g  | 1808                 | 1633                 | 1970                 | 3914             | 2421             | 3703             | 1730            | 4123             |
| Final Weight, g  | 976                  | 1077                 | 1316                 | 3253             | 1006             | 752              | 189             | 608              |
| Weight Loss, g   | 832                  | 556                  | 654                  | 661              | 1415             | 2951             | 1541            | 3515             |
| Weight Loss, %   | 46.2                 | 34.0                 | 33.2                 | 16.9             | 58.4             | 79.7             | 89.1            | 85.2             |
| Extinguish Time, minutes                                     | 21:20                | 10:50                | 9:34                 | 3:40             | 3 Hrs+ *         | ~5 Hrs           | 3:28 Hrs        | 7:34 Hrs         |

\* Test terminated by closing off all vents at 3 Hrs.

The values of merit in this test series were (1) weight loss and (2) time to extinguishment. As expected, the modified FR-3709<sub>3</sub>, formulated for increased intumescences performed best (for its density), followed by standard FR-3709<sub>2</sub>. FR-3709<sub>1</sub> was formulated for reduced intumescence. The isocyanurate foam (FR-10112) would likely have been completely consumed, except that the test was extinguished blocking the pail vents after three hours.

The Isocyanurate, fiberboard, balsa and Redwood tests all ended when the fire was quenched or the available fuel was depleted. None of these overpack materials were self-extinguishing; they all require outside intervention or fuel consumption to extinguish the flame. Interestingly, ash cubes from the non-intumescent materials tended to remain “cubical”, though they become smaller as they are consumed where the intumescent cubes swell and close off ventilation paths.

## SUMMARY

Thermal protection using organic materials is certainly complex as these tests have illustrated. The “Oil Burner” methodology we describe, requires minimal instrumentation, is economical (inexpensive pails are readily available), can be used for materials characterization, package design, and for comparing production foam batches with their original qualification tests.

Foam density, thickness, and the production of an intumescent carbonaceous char are important variables. Our tests indicate that increasing foam density (increasing the mass loading) is always protective- even though foam thermal conductivity is greater at higher densities. Of course, impact energy absorption, cost, weight, and in today's world, even blast-wave mitigation<sup>2</sup> are major foam density drivers.

In these tests, we found the anoxic, near step-function weight loss occurring at ~354 °C (for FR-3700 foam) to be an ideal temperature indicator, yielding a sharp, degraded/non-degraded foam boundary, that preserves an accurate, maximum temperature record at the recession surface.

Simulating damaged foam by using randomly packed cubes, proved to be a rather severe method, but was remarkably discriminatory, and we believe relevant to damaged containers.

Finally, the more we learned from the tests conducted the more questions we raised. We did not investigate the effect of polymer heat of combustion, rate of heat release or oxygen index on foam performance. Nor did we investigate the quantity of heat transferred to the "payload"- though it should not be difficult to add a heat sink or calorimeter to the foam at any particular foam depth. Also left uninvestigated, was the use of refractory sheet materials arranged in parallel with foam, or the affect of burner (pool fire) temperature on intumescent char formation. These questions and others may be investigated at a later date

## **ACKNOWLEDGEMENTS**

We wish to thank Kenneth Erickson of Sandia National Laboratories for his many helpful comments... and his DSC. To Robert Sevasin for preparing the test articles, instrumentation, conducting the tests and recording the data. And to Jamie Guenthoer, molecular biologist, and full time post-grad student at the University of Washington who was a great help with graphics, style, and formatting.

## **REFERENCES**

1. Hypothetical accident conditions, US Nuclear Regulatory Commission, 10 CFR 71.73(c)(1-3)  
<http://www.nrc.gov/reading-rm/doc-collections/cfr/part071/part071-0073.html>
2. R. L. Woodfin, Using polyurethane foams (RPF) for explosive blast energy absorption in applications such as anti-terrorist defenses, SAND2000-0958, Sandia National Laboratories  
<http://www.prod.sandia.gov/cgi-bin/techlib/access-control.pl/2000/000958.pdf>
3. Hypothetical accident conditions, US Nuclear Regulatory Commission, 10 CFR 71.73(c)(4)  
<http://www.nrc.gov/reading-rm/doc-collections/cfr/part071/part071-0073.html>



4. LAST-A-FOAM® FR-3700 and FR-6700 series rigid polyurethane urethane foams, General Plastics Manufacturing Company, Tacoma Washington, USA  
<http://www.generalplastics.com>
5. US Federal Aviation Administration, DOT/FAA/AR-12, Aircraft Fire Test Handbook  
[http://www.fire.tc.faa.gov/pdf/handbook/00-12\\_ch7.pdf](http://www.fire.tc.faa.gov/pdf/handbook/00-12_ch7.pdf)
6. Thermogage® water cooled circular foil heat flux transducer, Vatel Corporation
7. A.M. Birk, TP 13539E, Review of AFFTAC Thermal Model, Transport Canada, January 2000, Page 25 [http://psc.tamu.edu/database/thermal\\_model.pdf](http://psc.tamu.edu/database/thermal_model.pdf)
8. M. L. Hobbs, K.L. Erickson, T.Y. Chu, Modeling Decomposition of Unconfined Rigid Polyurethane Foam, page-33 SAND99-2758. Sandia National Laboratories,  
[http://infoserve.sandia.gov/sand\\_doc/1999/992758.pdf](http://infoserve.sandia.gov/sand_doc/1999/992758.pdf)
9. J. A. Elliott, J. L. Windle, “A dissipative particle dynamics method for modeling the geometrical packing of filler particles in polymer systems” Journal of Chemical Physics, Volume 113, Number 22. 2004/12/8

#### FOOTNOTE

---

<sup>i</sup> A previous revision of this paper was presented by Charles Williamson at PATRAM 2004 in Berlin Germany.